

Thermal desorption of molecular oxygen from SnO₂ (110) surface: Insights from first-principles calculations

Viacheslav Golovanov^{a,b,*}, Viktoria Golovanova^a, Tapio T. Rantala^b

^a South-Ukrainian University, Staroportofrankovskaya Str., 26, 65008, Odessa, Ukraine

^b Tampere University of Technology, P.O. Box 692, FI-33101 Tampere, Finland

ARTICLE INFO

Article history:

Received 22 May 2015

Received in revised form

11 October 2015

Accepted 20 October 2015

Available online 21 October 2015

Keywords:

A. oxides

B. ab initio calculations

C. surface properties

ABSTRACT

First-principles density functional theory calculations in the generalized gradient approximation, with plane wave basis set and pseudopotentials, have been used to investigate the desorption pathways of molecular oxygen species adsorbed on the SnO₂ (110) surface. Energetics of the thermodynamically favored precursors is studied in dependence on the surface charge provided either by surface defects or by donor type impurities from the near-surface region. The resonant desorption modes of O₂ molecules are examined in the framework of *ab initio* atomic thermodynamics and relationship of these results to experimental observations is discussed.

© 2015 Elsevier Ltd. All rights reserved.

1. Introduction

Tin dioxide (SnO₂) has been recognized as an attractive material with excellent optical properties, chemical durability, and transparent conductivity [1]. One crucial aspect governing the chemical behavior of SnO₂ is the chemistry associated with oxygen species adsorbed on the thermodynamically most stable (110) surface. The studies based on density functional theory (DFT) indicate that electronic charge transfer to the adsorbates is required to chemisorb oxygen atoms and molecules on the stoichiometric SnO₂ (110) surface [2]. The stabilization of neutral oxygen species is endothermic. For this reason, most of the theoretical calculations that deal with the interaction SnO₂ ··· O₂ have been performed for the reduced (110) surface with bridging (O_{br}) oxygen vacancies [2–6]. It is generally accepted that O₂ adsorbs at O_{br} vacancy sites and acquires negative charge donated by such surface defects. At elevated temperatures oxygen molecules dissociate to fill O_{br} vacancies and form adsorbed oxygen monoatoms at adjacent five-fold coordinated tin sites (Sn_{5c}) on the SnO₂ (110) surface [3].

It should be noted however that the direct scanning tunneling microscopy (STM) observations on the TiO₂ (110) surface which is isostructural with the SnO₂ surface are at variance with these previously proposed models that are based on O_{br} vacancies as the main charge donors [7]. Lira et al. [8] estimated that more than 90% of the electronic charge withdrawn by the oxygen adsorbates stems from charge donors in the near-surface region. Besides, STM images reveal

that O₂ molecules are found on top of Sn_{5c} atoms that constitute troughs along the [001] direction. Such conclusions correlate with temperature-programmed desorption (TPD) experiments, indicating that the full O₂ coverage at a low temperature (120 K) would be approximately three times the surface vacancy population [9]. The authors inferred that adsorbed O₂ molecules may exist either in weakly (below 200 K) or strongly (above 400 K) bound states. Therefore, the corresponding ionosorption channels for molecular oxygen can be associated with Sn_{5c} troughs and O_{br} vacancies, respectively.

In the chemisorbed-precursor mechanism the incident oxygen molecule initially adsorbs intact and the subsequent interplay between the thermally driven kinetics and the lack of surface electronic charge determines the pathways for O₂ desorption, chemisorption or dissociation. Although the excess charge can be donated by various donor type defects, the most of the DFT studies have been performed on the reduced SnO₂ (110) surface, where O₂ adsorption is mediated by the presence of surface O_{br} vacancies. The role of subsurface defects in providing an excess electrons for the SnO₂ ··· O₂ interaction is still unsettled today.

Earlier we have investigated computationally the effects of surplus electrons on the oxidized SnO₂ (110) surface with molecular oxygen adsorbed along the Sn_{5c} rows [10]. Now we compare the surface energetics of these superoxide molecules in conditions where an additional charge is generated by the presence of surface O_{br} vacancies or extrinsic donor type defects from the near-surface regions. The choice of fluorine dopant as the representative donor defect for tin dioxide is based on the previous works, where fluorine appears as a shallow donor, providing extra charge to the crystal.

In the meantime, the oxygen species adsorbed at SnO₂ surface

* Corresponding author. Tel.: +38 048 7668323; fax: +38 048 7770177.

E-mail address: alban@te.net.ua (V. Golovanov).

have only been studied in the zero temperature approximation, i.e., by neglecting vibrational and entropy contributions. In principle, the parameters of desorption channels for adsorbed O_2 molecule are significantly temperature dependent. In the present paper we examine the effects of the adsorbate motion on the thermally activated bond breaking and assess the calculated vibrational bond-stretching modes by correspondence with the available experimental evidences. The study of O_2 molecules weakly bound along the rows of five-fold coordinated surface tin atoms, which likely are precursors to desorbed gas phase O_2 molecules, allows us to better understand the sequence of elementary steps involved in thermally stimulated desorption of molecular oxygen from the SnO_2 surface.

2. Models and methods

A unit cell Sn_4O_8 is chosen for modeling of the (110) crystal surface instead of the conventional primitive cell Sn_2O_4 with different orientation. The computational supercell $(Sn_4O_8)_{10}$ is a $2 \times 5 \times 1$ multiple of the chosen unit cell. The surface of SnO_2 is therefore represented by three-dimensional periodic slab, consisting of five $O(Sn_2O_2)O$ layers periodic in the [001] and [1 $\bar{1}$ 0] directions, but finite in the [110] direction. All surfaces are modeled with a vacuum thickness exceeding 12 Å between the slabs. Test calculations were performed with supercell of $(Sn_4O_8)_{20}$, which is a $2 \times 5 \times 2$ multiple of the chosen unit cell. No appreciable differences in relaxed surface geometry and binding energy values were found in simulations where more empty space and larger supercell were used. The middle layer is kept fixed in bulk geometry while all other atoms relax in geometry optimization. Adsorption was allowed on only one of the two sides of the slab used to construct the SnO_2 (110) surface. The calculated coverage of O_2 on the surface is one molecule per supercell, which corresponds to 0.4 of a monolayer. The binding energy of O_2 adsorbate (E_b) is estimated as total energy difference of the supercells with O_2 molecule adsorbed on the surface and O_2 molecule located in the vacuum region of the supercell far from the surface.

Most calculations are based on the plane wave basis set with pseudopotentials as implemented in CASTEP code [11]. Use of ultrasoft pseudopotentials [12] enables us to limit the plane wave basis set to cutoff of 400 eV. Oxygen atoms are described by six valence electrons and tin atoms by four, plus the corresponding pseudopotential ion cores. Electronic exchange and correlation are included by the Perdew–Burke–Ernzerhof (PBE) generalized gradient approximation (GGA) allowing possible spin polarization [13]. The Brillouin zone is sampled with $3 \times 1 \times 3$ mesh of Monkhorst-Pack special k points. In separate test calculations, the number of irreducible k-points was increased up to 6 ($2 \times 2 \times 3$ mesh), which does not alter the obtained results. For charged systems, the negative charge of the unit cell is balanced by using constant background positive charge density. The Bader charge analysis has been carried out by means of the VASP package [14] and the projector augmented wave cores [15] with the cutoff set to 700 eV. The VASP software also allows to use of hybrid PBE0 functional, which reproduces the experimental band gap of 3.6 eV. In several complementary calculations, the PBE0 functional has been used against the GGA-PBE scheme in order to check the effect of the band gap underestimation on the reliability of the calculated adsorption energies. The calculated equilibrium lattice constants for bulk SnO_2 are $a=4.83$ Å, $c=3.23$ Å for PBE and $a=4.75$ Å, $c=3.18$ Å for PBE0.

In the transition level calculations, the O_2 molecules adsorbed on the SnO_2 surface were treated as surface defects, in the same framework successfully used for bulk defects in semiconductors [16]. Similarly, the formation energy (E_f) of an oxygen molecule in

charge state q adsorbed on the SnO_2 is defined as:

$$E_f = [E^{tot}(SnO_2 + O_2, q) - E^{tot}(SnO_2)] + \mu(O_2) + q\varepsilon_F, \quad (1)$$

where $E^{tot}(SnO_2 + O_2, q)$ and $E^{tot}(SnO_2)$ represent the total energies of the slab with adsorbed O_2 molecule in the charge state q , and that of a pristine slab in the same supercell. We consider that the surface of a slab is in equilibrium with an oxygen reservoir characterized by the chemical potential of oxygen $\mu(O_2)$, which we approximate with the total energy of one O_2 molecule in the vacuum. In order to change the charge state of the defect, electrons are exchanged with the Fermi level ε_F , which in semiconductors is referenced to the valence-band maximum and ranges over the band gap from the valence band maximum (E_V) up to the conduction band minimum (E_C). The Fermi energy values for which the occupation number of an adsorbed O_2 state in the energy gap changes from n to $n+1$ are given by the Fermi energy position where the formation energies of the n and $n+1$ charge-states of the O_2 are equal. Thus, electronic levels induced by the adsorbed O_2 molecule in the SnO_2 band gap can be investigated by calculating the O_2^0/O_2^- transition level. The potential alignment and finite-size correction were included according to scheme proposed in [17,18].

3. Results and discussion

3.1. Origin of electronic charge and binding energy

The schematic representation of the oxygen molecules adsorbed at bridging oxygen vacancy and neighboring Sn_{5c} sites are shown in Fig. 1. These are similar to the conformations reported in other first-principles calculations performed on rutile (110) surfaces of SnO_2 and TiO_2 [2–5,19–25]. At O_{br} vacancy the molecular oxygen adsorbs in peroxo form (O_2^{2-}) (Fig. 1(a,b)) and it is bound onto the SnO_2 surface strongly enough, so that it may desorb only after activation by thermal energy at temperatures higher than 400 K. Lira et al. [8] propose that an impinging O_2 molecule dissociates if it directly hits the O_{br} vacancy site. The intermediate structure, in which O_2 is located halfway between the vacancy and the Sn_{5c} sites, is presented in Fig. 1(c). For studies of the thermally stimulated O_2 desorption pathways, however, the less stable conformations associated with Sn_{5c} sites (Fig. 1(d–f)) are the most promising.

We first focus on the ionosorbed oxygen molecule bridging two Sn_{5c} atoms and lying parallel to the surface along the [001] direction (Fig. 1(d)). The plausibility of this configuration has been revealed in fast-scanning STM observations [26]. The calculated bonding and electronic structure parameters of O_2 adsorbate are compared in Table 1 for the following molecule-surface systems: (i) the supercell, where one to six lattice oxygen atoms are substituted by the fluorine dopants (F_O), (ii) the supercell with one to three O_{br} vacancies, (iii) the supercell, where F_O and O_{br} vacancy are presented jointly, and (iv) the supercell, where additional electrons are provided using the model with constant background positive charge density.

The calculated binding energy of oxygen molecule and SnO_2 slab with one O_{br} vacancy (0.43 eV) or one surplus electron (0.41 eV) corroborates results reported previously by Oviedo et al. [2]. It can be seen however that interaction of adsorbed O_2 with SnO_2 surface strongly depends on the origin and amount of the surface excess charge.

The most prominent surface relaxation associated with such conformation is a downward displacement (0.55 Å) of the nearest to adsorbed O_2 molecule surface in-plane oxygen atoms. From the partial density of states (PDOS) projected on the adsorbed O_2^- we

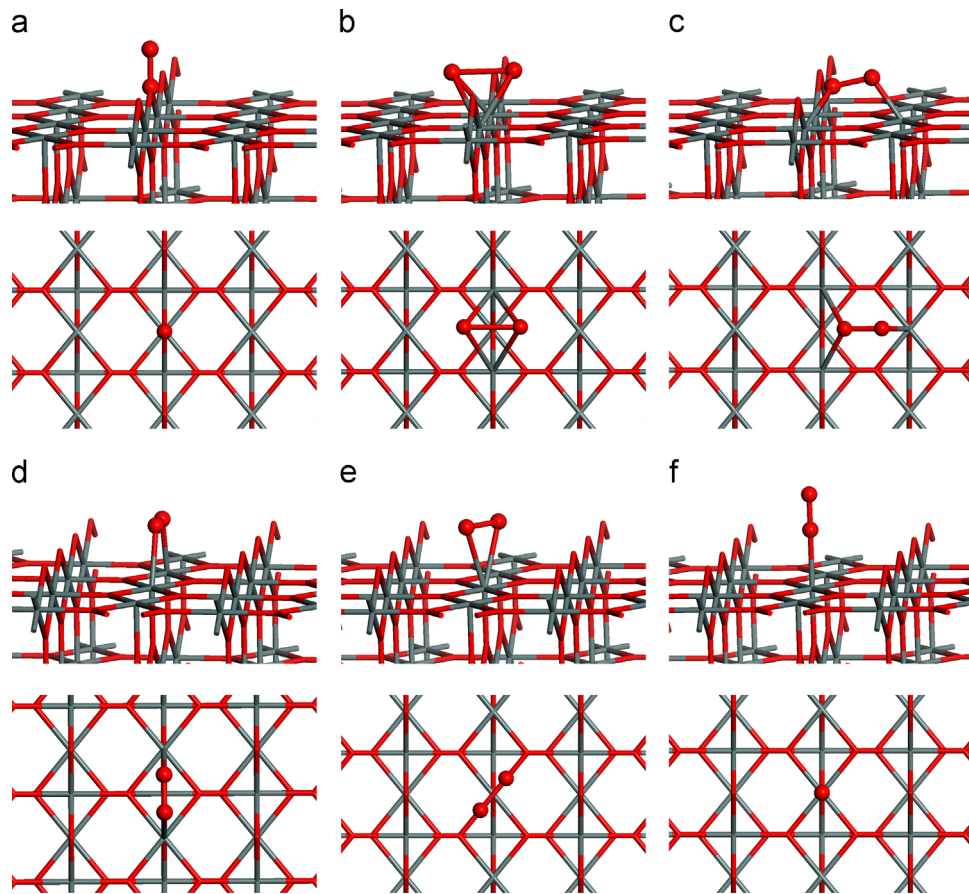


Fig. 1. The side and top views of the molecular oxygen adsorption structures adsorbed at SnO₂ (110) surface. Sn and O atoms of the slab are represented as gray and red sticks, respectively, while adsorbed O atoms are represented as red spheres. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article)

find that molecular π_g^* Kohn-Sham levels lie above the E_V , thus suggesting the existence of an acceptor level in the SnO₂ energy gap. The perpendicular to the surface π_g^* orbital ($\pi_g^{\perp}$) is fully occupied, while the parallel to the surface π_g^* orbital ($\pi_g^{\parallel}$) is filled for only spin-up electron, thus exhibiting spin polarization. The charge transfer to the $\pi_g^{\parallel}$ antibonding O₂ orbital is confirmed by similar isosurfaces of the spin density distribution shown in Fig. 2 and the highest occupied molecular orbital (HOMO) of O₂, which electron cloud is perpendicular to the axis of oxygen molecule. Thus, in abundance of surface free charge carriers the charge transfer from the substrate to the molecule quenches its spin density to $\sim 1.0 \mu_B$, which is half of the magnetic moment possessed by the gas-phase O₂. The O–O bond of the parallel precursor is lengthened up to about 7% of the gas-phase O₂ bond length. These results indicate that the oxygen molecule is adsorbed through a chemisorption mechanism in superoxo like form (O₂[−]).

The amount of surface charge, however, has strong impact on the value of the calculated binding energy of the adsorbed oxygen

molecule. Earlier we have demonstrated that substitutional fluorine donor provides an extra charge to the crystal, which is delocalized in the perfect bulk [27,28]. The Bader charge analysis indicates that F_O donates only a fraction of the electron (0.33e) to the conduction band. Approximately 0.66e is localized at F_O defect, deep in the band gap, and such electron density is not affected neither by O₂ adsorption nor by calculations of the host with one hole ($q = +1$). Thus more than one fluorine defect is needed to firmly stabilize superoxide at SnO₂ surface. Furthermore, interaction of the tin dioxide with oxygen molecule adsorbed in a selected configuration apparently has electronic and magnetic components, which are strongly dependent on the amount of excess electrons.

From the density difference plot (not shown) we deduce that neutral O₂ molecule, placed above the five-fold tin sites on the perfect stoichiometric slab, acquires fractional charge on its HOMO from the substrate, thus, causing electron deficiency on the surrounding surface atoms. This leads to induction of magnetic moments on the nearest to adsorbate O_{br} atoms and ferromagnetic

Table 1
Summary of the results from calculations of O₂ adsorbed at Sn_{5c} through in a parallel orientation.

Supercell with:	(i) F _O impurity					(ii) O _{br} vacancy			(iii) F _O +O _b	(iv) extra e [−]	
Number of defects	1	2	3	4	6	1	2	3	1+1	“−1”	“−2”
Binding energy, (eV)	0.19	0.27	0.41	0.56	0.81	0.43	0.61	0.62	0.59	0.41	0.58
Length of O ₂ bond (Å)	1.31	1.32	1.32	1.32	1.32	1.32	1.33	1.36	1.32	1.32	1.33
Spin density for O ₂ (μ _B)	0.99	1.00	1.02	1.02	1.04	1.00	1.00	0.82	0.98	1.00	1.01
Spin density for O _{br} (μ _B)	0.20	0.14	0.10	0.05	0.00	0.25	0.01	0.00	0.01	0.04	0.00

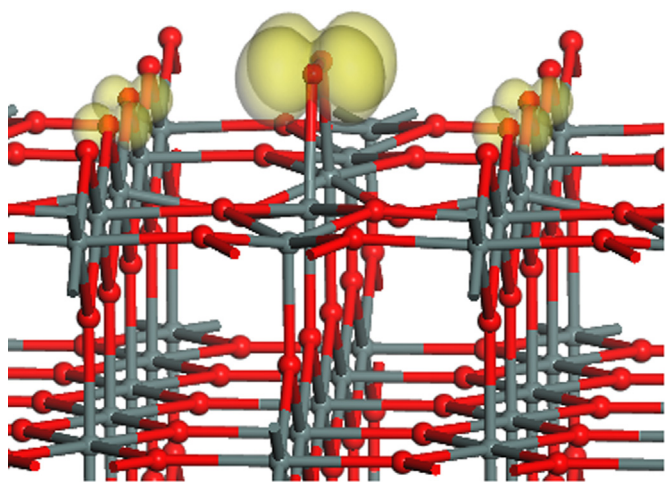


Fig. 2. Isosurface of spin density distribution (contoured at $0.05\text{e}^{-}\text{\AA}^{-3}$) for superoxide O_2^- molecule adsorbed at Sn_{5c} trough.

coupling between them and O_2 . This behavior is similar to the scenery of the adsorbed O_2 in the negatively charged supercell, as illustrated in Fig. 2. Such oxygen molecule at the stoichiometric (110) surface is metastable with endothermic energy of 0.4 eV. In slab with electron donors (F_O or O_{br} vacancies), the chemisorbed oxygen molecule withdraws one electron from SnO_2 substrate onto its antibonding π_g^* orbital, which is at resonance with the Fermi level. However, in systems featured by the lack of surface electronic charge, like supercell doped with a single fluorine atom, a weak magnetic coupling between O_2^- and neighboring O_{br} atoms is still observed. This magnetic interaction destabilizes superoxide at SnO_2 (110) surface and eventually reduces its adsorption energy. As follows from the results summarized in Table 1, an accumulation of the surface surplus charge quenches spins on the O_{br} atoms, and accordingly, gives rise to E_b of the adsorbate. In other words, even if O_2 molecule has already accepted one electron from the substrate, more charge is needed for quenching the magnetic interaction and further stabilization of the adsorbate. The obtained results can be rationalized assuming that adsorbed O_2 molecule breaks stoichiometry of the slab and can be considered in reality as a surface fractional cation vacancy, which according to our recent results [29] can induce magnetism in the nearest oxygen atoms.

In principle, electronic charge acquired by the adsorbate may originate from donor type defects with variant donor levels in the band gap. Typical donors are bulk and surface oxygen vacancies or fluorine and hydrogen impurities. Relative positions of the electronic levels of chemisorbed O_2 molecule and the main charge donors implicated in the calculations may affect the evaluation of the E_b . Indeed, the charge donated by F_O impurity is delocalized in the conduction band, while bridging oxygen vacancies form the surface states, which trap electrons about 0.7 eV below the E_c [1]. Accordingly, in desorption of an O_2 molecule, the electron previously trapped at adsorbate becomes delocalized in the conduction band in the presence of F_O , but becomes localized at O_{br} vacancy in case of the reduced SnO_2 surface, making a notable difference in E_b . The calculated E_b based on the total energy difference is therefore higher in the former case, where additional charge is generated by the shallower donor type defects. This constitutes an ambiguity in calculation of the O_2 binding energy, which depends on the origin of the electronic charge provided by the different donor type defects mediating adsorption of O_2 molecule.

Calculated saturation of E_b with increasing number of O_{br} vacancies in the supercell reveals that the released electron density

remains localized mainly at the vacancy sites in desorption. Mulliken population analysis indicates, however, that certain fraction of the electronic charge populates the surface Sn_{5c} that constitute E_c due to broadened occupation with Gaussian like smearing (width of 0.1 eV). This may explain close values of the binding energy calculated for the slabs, where sufficient additional charge is provided by four fluorine impurities (0.59 eV) or two O_{br} vacancies (0.61 eV). On the other hand, we find that Fermi level is profoundly shifted to the conduction band in the slab with six fluorine dopants thus giving unreasonable rise to the E_b . Based on the results summarized in Table 1, the proper binding energy for O_2 molecule is estimated to be around 0.6 eV. Remarkably, the activation energies experimentally calculated on SnO_2 films from Arrhenius plots measured in different oxygen partial pressure range from 0.56 to 0.65 eV in the temperature intervals corresponding to the stimulated desorption of oxygen species from the samples [30].

The transition state $\text{O}_2^\circ/\text{O}_2^-$ calculated with PBE functional points to a deep level in the band gap ($E_\text{v} + 0.33$ eV). This corroborates findings of Bonapasta et al. [31], based on the thermodynamic DFT approach and the same PBE functional. For O_2 molecule adsorbed at Ti^{+4} sites of (100) TiO_2 anatase surface they found transition energy level at $E_\text{v} + 0.29$ eV. Such a deep position of the charge transition state for O_2 molecule would imply a high barrier to desorption. It is at variance with both E_b determined above from the total energy difference and experimental observations. These discrepancies can obviously be related to the underestimation of the band gap in thermodynamic DFT approach based on PBE functional. In order to validate E_b obtained at GGA-PBE level, we have performed the band gap corrected calculations with hybrid PBE0 functional for the supercells featured by the presence of one and two O_{br} vacancies. Found binding energies based on total energy differences (0.61 and 0.64 eV, respectively) are in line with our previous findings for the systems featured by abundance of the surface electronic charge. It can be concluded that use of the hybrid functional is very important for the correct estimation of the position of $\text{O}_2^\circ/\text{O}_2^-$ transition level in the band gap by thermodynamic approach. On the other hand, the choice of the functional does not essentially affect the adsorption energy calculated from the total energy difference scheme.

3.2. Finite temperature effects

Accounting the adsorbate motion provides complementary insight into the thermally stimulated desorption of O_2 precursors from SnO_2 surface. According to Warren [32], the root mean square (RMS) displacement of atoms in crystal due to thermal vibrations turns out to be of the order of 0.2 Å. It was deduced that the displacements at room temperature are of the order of 5% of the nearest neighbor distance. From Mössbauer spectroscopy measurements of tin oxide films, the RMS displacement of the Sn atom normal to the surface is estimated to be about 0.13 Å at 213 K [33]. Thermal studies of SnO_2 nanoparticles by X-ray diffraction and Rietveld analysis [34] give RMS value up to 0.25 Å at room temperature. Typically atoms in small nanoparticles exhibit higher RMS displacement due to high surface-to-volume ratio [35]. We did not find RMS data for molecular adsorbate on SnO_2 surface, but would expect it to be comparable or even higher than above-mentioned values due to broadened degrees of freedom. Thus, the chosen in the simulations mutual adsorbate – surface fluctuations of 0.2–0.3 Å comply with experimental observations at room temperatures.

Since the experimental desorption times of $\text{SnO}_2 \cdots \text{O}_2$ system are longer than the simulation time scales accessible to the most efficient *ab initio* molecular dynamics schemes, we prepare the snapshot configurations by introducing small displacements of the oxygen atoms of the adsorbed O_2 molecule. We consider

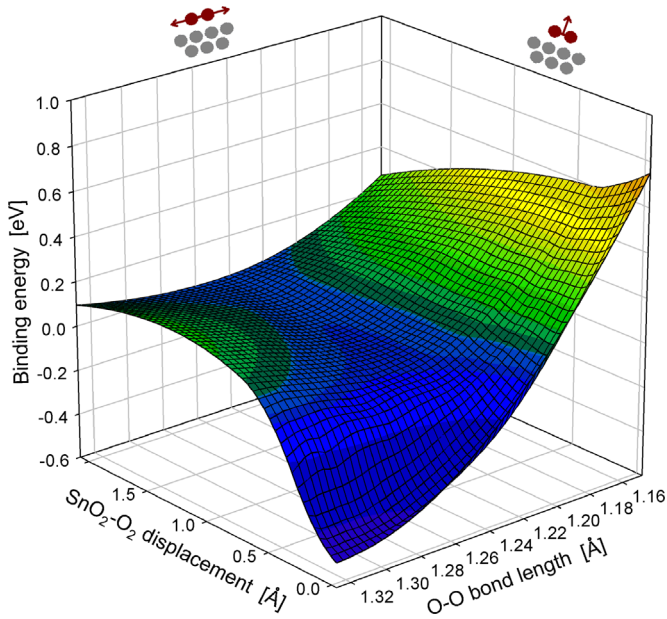


Fig. 3. The calculated potential-energy surface representing the binding energy of oxygen molecule adsorbed at the SnO_2 Sn_{5c} through as a biaxial function of O–O bond length and displacement of O_2^- center of mass from its optimized position, induced by vibration modes.

displacements to opposite directions from the equilibrium positions and calculate the change in total energy versus offset.

In the case of O_2 molecule lying parallel to the surface, the O–O bond length and the distance of O_2 center of mass from the fixed centermost atomic layer are chosen as the reaction coordinates of the desorption pathway. Thermally stimulated desorption of molecular oxygen is explored first on the relaxed surface with fixed equilibrium lattice constants. The effect of surface strain is then investigated by compressed or stretched lattice constants, whereon various properties are calculated again.

The calculated binding energy of O_2 adsorbed on the SnO_2 surface as a biaxial function of SnO_2 – O_2 and internal O–O distances is presented in Fig. 3. The change in energy versus variable position results in a potential-energy surface, from which we determine the O–O stretching frequency and desorption frequency factor (ν) using the harmonic oscillator approximation. The vibrational frequency of the O–O stretching mode is red shifted with respect to free O_2 molecule (1580 cm^{-1}) and is found to be 1140 cm^{-1} . This is in good agreement with experimentally measured vibration frequencies of O_2^- adsorbed on SnO_2 surface (1045 cm^{-1} and 1190 cm^{-1}) [36]. The critical displacement at which O_2^- is discharging upon lifting from the surface amounts approximately to 0.4 Å as traced by Mulliken population analysis. In this transition state the magnetic moment of oxygen molecule increases from $\sim 1.0\text{ }\mu_B$ to $2.0\text{ }\mu_B$, which is characteristic of the gas phase O_2 molecule in triplet state. Before that the binding energy increases with distance by quadratic law. The calculated value of ν is therefore estimated as $2 \times 10^{11}\text{ s}^{-1}$, which is two orders of magnitude lower than the frequency factor (10^{13} s^{-1}) provided by the classical Eyring's theory [37], but two orders of magnitude higher than values 2×10^8 – $3 \times 10^9\text{ s}^{-1}$, obtained for $\text{SnO}_2 \cdots \text{O}_2$ system in TPD experiments [38]. These differences illustrate some limitations of the TPD methods based on peak maximum temperatures and described elsewhere [38,39]. On the other hand, it is known that GGA-PBE calculations overestimate the vibrational frequencies by several percent [40].

The phenomenological treatment of individual and collective effects of the adsorbate on the transducer function of semiconductor sensor has been reported by us elsewhere [41]. In the

framework of the Volkenstein model [42], the thermal activation of an electron from the chemisorption state into the conduction band (in the case of an acceptor type surface defect) is considered as the precursor for desorption of the neutral molecule, if the lifetime of the physisorbed state is assumed to be negligible. By contrast, the time-dependent DFT approach applied recently to the TiO_2 – O_2 system [43] predicts the lifetime of excited O_2 molecule, i.e., the state, in which the electron trapped by adsorbed O_2 molecule is injected back into the substrate, to be 266 fs. The calculated lifetime is short enough as compared with characteristic time of the O_2 precursor (50 ms) evaluated from the pre-exponential frequency factor (ν) that points out on the high probability of readsorption, which may occur in case if excess electronic charge is available at the surface. This process is not taken into account in TPD measurements based on peak maximum temperatures.

The readsorption occurs efficiently if free electrons are available at the surface, e.g., in case of SnO_2 doped with fluorine impurity. With F_0 defects as the main charge donors the additional charge is delocalized in the conduction band and can be readily retrapped by excited O_2 molecule. While O_{br} vacancies also provide the surface excess electrons, the extra charge is mainly localized around the defects. Being a surface trapping centers, the bridging oxygen vacancies can capture electrons released by oxygen species thus reducing the probability of O_2 readsorption.

Analysis of Fig. 3 indicates that contribution of the O–O stretching mode to decrease the adsorption barrier is approximately twice lower than that of the center-of-mass (SnO_2 – O_2) mode. The 5% compression of the O–O bond leads to reduction of E_b on 0.16 eV, while 5% displacement of the O_2 center of mass from its optimal position on the SnO_2 surface is accompanied by diminishing of the adsorption barrier on 0.3 eV. Such behavior implies that coupling between the p-orbitals of oxygen molecule is less sensitive to the thermal motion than $\pi_g^\perp$ hybrid formed between p-orbital of O_2 molecule and s-orbital of the surface Sn_{5c} atom, apparently because of the more delocalized character of Sn s-states in s–p hybrid as compared with anion p-states, where directional bonding plays significant role.

When oxygen molecule vibrates on the surface, the position of the π_g^* resonances relative to the ϵ_F also oscillates, which also means large fluctuation in the occupation numbers of π_g^* orbitals. The calculated shifts of the O_2^- $\pi_g^\parallel$ HOMO and the $\pi_g^\perp$ hybrid orbital as a function of dynamic snapshots for different fully relaxed adsorbate-surface conformations upon lifting of the O_2^- from its equilibrium position are presented in Table 2. The internal stretching vibrations of the O_2 molecule are reflected in strong ($\sim 3\text{ eV}$) fluctuation of its antibonding $\pi_g^\parallel$ and $\pi_g^\perp$ Kohn-Sham levels with respect to the deep $1\sigma_g$ orbital of the same molecule, while variation of the $\pi_g^\parallel$ resonance relative to the 5 s orbitals of the Sn_{5c} surface sites is less pronounced and amounts to 0.5 eV. As expected, the $\pi_g^\perp$ orbital exhibits the largest upshift of 1.5 eV

Table 2

The calculated from PDOS shifts in energies (eV) of the $\pi_g^\perp$ hybrid orbital; the $\pi_g^\parallel$ HOMO and the $\pi_g^\parallel$ LUMO caused by the displacement of the center of mass (ΔR) of the chemisorbed O_2^- molecule from its optimal position on the SnO_2 surface. Positive values correspond to upshift in position of the orbital.

ΔR , Å	Relative to the O_2 $1\sigma_g$ -orbital		Relative to the Sn_{5c} 5 s-orbitals	
	$\pi_g^\perp$	$\pi_g^\parallel$ HOMO	$\pi_g^\perp$	$\pi_g^\parallel$ HOMO
0.1	0.10	0.14	0.18	0.21
0.2	0.18	0.23	0.28	0.32
0.3	0.85	0.96	0.53	0.43
0.4	1.90	1.80	0.92	0.48
0.5	2.72	2.65	1.18	0.53
0.6	2.90	2.85	1.39	0.55
0.7	3.05	2.92	1.52	0.52
0.8	3.10	2.99	1.54	0.49

in response to displacement of the oxygen molecule. This points to a possible local synergetic effect of the mutual vibration of O_2^- and Sn_{5c} surface atoms underneath, on the charge oscillations between the molecular $\pi_g^\perp$ resonance and the substrate.

In order to evaluate the effect of surface strain on the thermochemistry of O_2 desorption we used lattice constants 2% less than the equilibrium values to model a compressed surface and 2% more than the equilibrium values to model a stretched surface. We find that surface contraction increases stability of the O_2 adsorbate, while lattice expansion implies a lower barrier to desorption due to the lower binding energy of O_2 with Sn_{5c} surface sites. This can be explained by the fact that the s-s and s-p bonds are more sensitive to the bond length deviations, than p-p bonds, because of the more delocalized character of the s-orbitals. The mutual displacement of the surface atoms driven by the finite temperature effects leads to a variation in the relative positions of the E_C , formed by 5s orbitals of tin atoms, and the s-p hybrid $\pi_g^\perp$ orbital of the O_2 molecule, which has a significant effect on the O_2 molecule adsorption energy. The surface stretching of 2% leads to E_b of only 0.05 eV, while the trapped electron is still found on the oxygen molecule. The further injection of the electron into the conduction band induced by the thermally stimulated adsorbate-surface motion has high probability.

The PDOS reflecting the effect of surface strain are presented in Fig. 4. The surface expansion of 2% causes downshift (0.5 eV) of the

Sn 5s-orbitals, while all π_g^* levels of the chemisorbed O_2^- molecule move slightly upward (0.06 eV). Surface compression of 2% leads to increase in energy of the Sn s-orbitals on 0.4 eV. The $\pi_g^\perp$ and the $\pi_g^\parallel$ HOMO behaves similarly and move down in the band gap on 0.47 eV, while $\pi_g^\parallel$ LUMO is shifting down on only 0.06 eV. The strong variation of the Sn edge states induced by the thermal expansion corroborates results of Li et al. [44], where a small isotropic strain changes the SnO_2 band gap as much as 0.8 to 1 eV. The similar downshift of the occupied $\pi_g^\perp$ and $\pi_g^\parallel$ orbital levels induced by the surface contraction reflects stabilization of the adsorbate due to stronger ionic bonding with surface [45]. The coupling of $\pi_g^\parallel$ LUMO with Sn 5s-orbitals constituting the E_C upon surface expansion indicates, that in abundance of the surface free carriers, the desorption of O_2 molecule can be additionally stimulated by capturing of an extra electron on its antibonding $\pi_g^\parallel$ orbital.

The surface quasiharmonic (volumetric) contribution to the O_2 desorption pathway dominates the effect arising from the thermal motion associated with the center-of-mass (SnO_2-O_2) mode, which in turn is twice stronger than the effect of the O–O internal stretching mode. The aggregate fluctuation of the π_g^* resonances due to thermal broadening and mutual vibrations of O_2 molecule and surface can reach 1 eV. This value is comparable with calculated adsorption energy (0.6 eV) of O_2 molecule, which implies lowering or even vanishing of the activation barrier to desorption

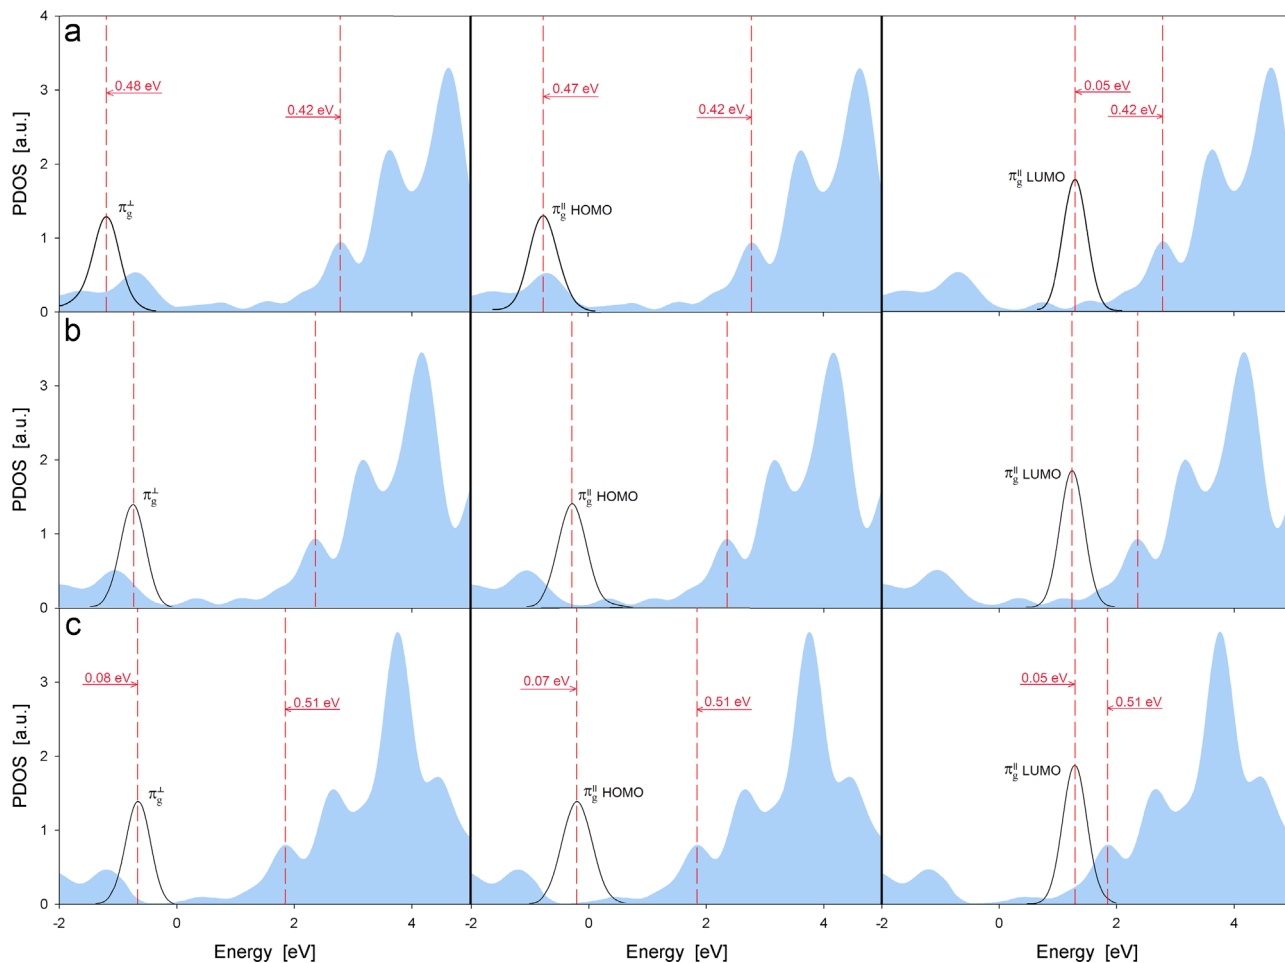


Fig. 4. The PDOS of the Sn_{5c} surface atoms (blue area) and the PDOS of the $\pi_g^\perp$ hybrid orbital (left panel); the $\pi_g^\parallel$ HOMO (center panel) and the $\pi_g^\parallel$ LUMO (right panel) of the O_2^- molecule adsorbed on-top of the Sn_{5c} surface atoms (black line) calculated for (a) compressed by 2% surface, (b) surface with equilibrium lattice constants, and (c) surface stretched by 2%. The red arrows indicate direction and values of the shifts in the energetic position of the corresponding orbitals. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article)

at finite temperatures. Accounting the vibrational contributions can provide insight into the low-temperature (below 200 K) desorption of O_2 molecules from SnO_2 surface, notwithstanding that the adsorption energy of oxygen species is noticeable.

4. Conclusions

In summary, we find that oxygen molecules adsorb in superoxide like form (O_2^-) on SnO_2 (110) surface on top of the fivefold coordinated surface tin atoms. The binding energy strongly depends on the availability of surface free electrons. At lack of free electrons, the molecule induces magnetic moments on the nearest O_{br} atoms, which eventually destabilize the superoxide. In the presence of surplus electrons the adsorption energy of O_2 molecule is estimated to be about 0.6 eV. Therefore, these species can be associated with low-temperature (< 200 K) peak observed in the TPD experiments. We also demonstrate that the nature of main donor and the position of donor level with respect to the adsorbate electronic levels, in particular, has significant influence on the evaluation of the adsorption energy.

The finite temperature effects associated with the adsorbate-surface displacements have a strong impact on the position of antibonding π_g^* levels of the O_2^- molecule with respect to the Fermi level ϵ_F in SnO_2 . We found that fluctuations at magnitudes that may be achieved at room temperatures produce the energy changes comparable with the adsorption energy of O_2 molecule.

From comparison of the characteristic time of adsorbed O_2 precursor with the lifetime of oxygen molecule in excited state we deduce, that the surface electronic charge has also influence on the parameters of desorption through the readsorption channel. In other words, at lack of the electronic charge, the relatively slow thermally activated bond breaking processes (as compared to fast recharging) are the bottleneck of O_2 desorption. This is at variance with the well-known Volkenstein model, where electronic processes, and in particular, position of the ϵ_F in the band gap always dominates the kinetics of thermal desorption. It can be concluded that doping with shallow donor type defects, like fluorine or hydrogen, which leads to enrichment of the surface with excess charge, can substantially hinder the rate of molecular oxygen desorption.

We can draw the picture that describes the molecular oxygen desorption path as the following. At high temperatures in oxygen-rich limit, which is actually a favorable operation regime for the SnO_2 based chemical sensors, the oxygen atoms diffusing along the Sn_{5c} rows can recombine in weakly bound oxygen molecules, thus forming thermodynamically favorable precursors for the O_2 desorption pathway. This implies the second order desorption kinetics rather than first order kinetics observed in low-pressure TPD experiments performed under ultra-high vacuum conditions. The role of the donors or surface electronic charge is crucial for energetics and essential kinetic parameters.

Acknowledgment

This work was partially supported by FP7-PEOPLE Marie Curie International Incoming Fellowship Program (project MOEBIUS). Computational resources were provided by the CSC – IT Center for Science, Espoo, Finland.

References

- [1] M. Batzill, U. Diebold, The surface and materials science of tin oxide, *Prog. Surf. Sci.* 79 (2005) 45–154.
- [2] J. Oviedo, M. Gillan, First-principles study of the interaction of oxygen with the SnO_2 (110) surface, *Surf. Sci.* 490 (2001) 221–236.
- [3] B. Slater, C. Catlow, D. Williams, A. Stoneham, Dissociation of O_2 on the reduced SnO_2 (110) surface, *Chem. Commun.* (2000) 1235–1236.
- [4] F. Sensato, R. Custodio, M. Calatayud, A. Beltran, J. Andres, J. Sambrano, E. Longo, Periodic study on the structural and electronic properties of bulk, oxidized and reduced SnO_2 (110) surfaces and the interaction with O_2 , *Surf. Sci.* 511 (2002) 408–420.
- [5] M. Habgood, N. Harrison, An ab initio study of oxygen adsorption on tin dioxide, *Surf. Sci.* 602 (2008) 1072–1079.
- [6] M. Viitala, O. Cramariuc, T.T. Rantala, V. Golovanov, Small hydrocarbon adsorbates on SnO_2 (110) surfaces: Density functional theory study, *Surf. Sci.* 602 (2008) 3038–3042.
- [7] E. Lira, P. Huo, J. Hansen, F. Rieboldta, R. Bechsteina, Y. Wei, R. Strebera, S. Porsgaard, Z. Li, E. Lægsgaard, S. Wendt, F. Besenbacher, Effects of the crystal reduction state on the interaction of oxygen with rutile TiO_2 (110), *Catal. Today* 182 (2012) 25–38.
- [8] E. Lira, J. Hansen, P. Huo, R. Bechstein, P. Galliker, E. Lægsgaard, B. Hammer, S. Wendt, F. Besenbacher, Dissociative and molecular oxygen chemisorption channels on reduced rutile TiO_2 (110): An STM and TPD study, *Surf. Sci.* 604 (2010) 1945–1960.
- [9] M. Henderson, W. Epling, C. Perkins, C. Peden, U. Diebold, Interaction of molecular oxygen with the vacuum-annealed TiO_2 (110) surface: molecular and dissociative channels, *J. Phys. Chem. B* 103 (1999) 5328–5337.
- [10] M. Mätki-Jaskari, T.T. Rantala, V. Golovanov, Computational study of charge accumulation at SnO_2 (110) surface, *Surf. Sci.* 577 (2005) 127–138.
- [11] V. Milman, B. Winkler, J.A. White, C.J. Pickard, M.C. Payne, E.V. Akhmatkaya, R. H. Nobes, Electronic structure, properties, and phase stability of inorganic crystals: a pseudopotential plane-wave study, *Int. J. Quant. Chem.* 77 (2000) 895–910.
- [12] D. Vanderbilt, Soft self-consistent pseudopotentials in generalized eigenvalue formalism, *Phys. Rev. B* 41 (1990) 7892–7895.
- [13] J.P. Perdew, J.A. Chevary, S.H. Vosko, K.A. Jackson, M.R. Pederson, D.J. Singh, C. Fiolhais, Atoms, molecules, solids, and surfaces: Applications of the generalized gradient approximation for exchange and correlation, *Phys. Rev. B* 46 (1992) 6671–6687.
- [14] M. Marsman, J. Paier, A. Stroppa, G. Kresse, Hybrid functionals applied to extended systems, *J. Phys.: Condens. Matter* 20 (2008) 064201.
- [15] P. Blöchl, Projector augmented-wave method, *Phys. Rev. B* 50 (1994) 17953–17979.
- [16] P. Agoston, K. Albe, R. Nieminen, M. Puska, Intrinsic n-type behavior in transparent conducting oxides: A comparative hybrid-functional study of In_2O_3 , SnO_2 , and ZnO , *Phys. Rev. Lett.* 103 (2009) 245501–245504.
- [17] C. Freysoldt, J. Neugebauer, C.G. Van deWalle, Fully ab initio finite-size corrections for charged-defect supercell calculations, *Phys. Rev. Lett.* 102 (2009) 016402.
- [18] H.-P. Komsa, T.T. Rantala, A. Pasquarello, Finite-size supercell correction schemes for charged defect calculations, *Phys. Rev. B* 86 (2012) 045112.
- [19] U. Pulkkinen, T.T. Rantala, T.S. Rantala, V. Lantto, Kinetic Monte Carlo simulation of oxygen exchange of SnO_2 surface, *J. Mol. Catal. A: C* 166 (2001) 15–21.
- [20] A. Tilocca, A. Selloni, O_2 and vacancy diffusion on rutile (110): pathways and electronic properties, *Chem. Phys. Chem* 6 (2005) 1911–1916.
- [21] N. Zhanpeisov, H. Fukumura, Oxygen vacancy formation on rutile TiO_2 (110) and its interaction with molecular oxygen: A theoretical density functional theory study, *J. Phys. Chem. C* 111 (2007) 16941–16945.
- [22] M.D. Rasmussen, L.M. Molina, B. Hammer, Adsorption, diffusion, and dissociation of molecular oxygen at defected TiO_2 (110): A density functional theory study, *J. Chem. Phys.* 120 (2) (2004) 988–997.
- [23] H. Xu, S.Y. Tong, Interaction of O_2 with reduced rutile TiO_2 (110) surface, *Surf. Sci.* 610 (2013) 33–41.
- [24] M.P. de Lara-Castells, J. Krause, Theoretical study of the interaction of molecular oxygen with a reduced TiO_2 surface, *Chem. Phys. Lett.* 354 (2002) 483–490.
- [25] C. Shu, N. Sukumar, C. Ursenbach, Adsorption of O_2 on TiO_2 (110): A theoretical study, *J. Chem. Phys.* 110 (21) (1999) 10539–10544.
- [26] E. Wahlstrom, E. Vestergaard, R. Schaub, A. Ronnau, M. Vestergaard, E. Lægsgaard, I. Stensgaard, F. Besenbacher, Electron transfer-induced dynamics of oxygen molecules on the TiO_2 (110) surface, *Science* 303 (2004) 511–513.
- [27] N. Özcan, T. Kortelainen, V. Golovanov, T.T. Rantala, J. Vaara, Electron spin resonance parameters of bulk oxygen vacancy in semiconducting tin dioxide, *Phys. Rev. B* 81 (2010) 235202–235210.
- [28] V. Golovanov, M. Viitala, T. Kortelainen, O. Cramariuc, T. Rantala, Stability of siloxane couplers on pure and fluorine doped SnO_2 (110) surface: A first principles study, *Surf. Sci.* 604 (2010) 1784–1790.
- [29] V. Golovanov, V. Golovanova, M. Kuisma, T.T. Rantala, Electron spin resonance parameters of cation vacancies in tin dioxide doped with fluorine and hydrogen, *J. Appl. Phys.* 114 (2013) 143907.
- [30] V. Lantto, V. Golovanov, A comparison of conductance behavior between SnO_2 and CdS gas-sensitive films, *Sens. Actuators B* 25 (1995) 614–618.
- [31] A. Bonapasta, F. Filippone, Photocatalytic reduction of oxygen molecules at the (100) TiO_2 anatase surface, *Surf. Sci.* 577 (2005) 59–68.
- [32] B.E. Warren, X-ray Diffraction, Dover publications, New York, 1969.
- [33] J.F. Danielli, M.D. Rosenberg, D.A. Cadenhead, Progress in Surface and

- Membrane Science, Academic Press, New York, 1972.
- [34] N. Rajamanickam, R.N. Mariammal, K. Ramachandran, Thermal Studies on SnO_2 Nanoparticles, *Adv. Mat. Res.* 678 (2013) 67–71.
- [35] C.Q. Sun, Size dependence of nanostructures: Impact of bond order deficiency, *Prog. Solid State Chem.* 35 (2007) 1–159.
- [36] T.A. Gundrizer, A.A. Davydov, Infrared spectra of oxygen adsorbed on SnO_2 , *React. Kinet. Catal. Lett.* 3 (1975) 67–70.
- [37] R.I. Masel, Principles of adsorption and reaction on solid surfaces, John Wiley & Sons, New York, 1996.
- [38] D. Puzzovio, M.C. Carotta, A. Cervi, A. El Hachimi, J.P. Joly, F. Gaillard, V. Guidi, TPD and ITPD study of materials used as chemoresistive gas sensors, *Solid State Ion-* 180 (2009) 1545–1552.
- [39] J. Niemantsverdriet, K. Wandelt, The compensation effect in thermal desorption of adsorbate systems with lateral interactions, *J. Vac. Sci. Technol. A6* (3) (1988) 757–761.
- [40] A. Scott, L. Radom, Harmonic vibrational frequencies: An evaluation of Hartree–Fock, Møller–Plesset, quadratic configuration interaction, density functional theory, and semiempirical scale factors, *J. Phys. Chem.* 100 (41) (1996) 16502–16513.
- [41] V. Golovanov, V. Smyntyna, Interaction between collective and local subsystems in semiconductor surface-active structures, *Sens. Actuators B* 24–25 (1995) 647–652.
- [42] F. Volkenstein, Electronic processes on semiconductor surfaces during chemisorption, Consultants Bureau, New York, 1991.
- [43] P. Dholabhai, H. Yu, Electronic structure and quantum dynamics of photo-initiated dissociation of O_2 on rutile TiO_2 nanocluster, *J. Chem. Phys.* 138 (2013) 194705–194712.
- [44] H. Li, I. Castelli, K. Thygesen, K. Jacobsen, Strain sensitivity of band gaps of Sn-containing semiconductors, *Phys. Rev. B* 91 (2015) 045204–045206.
- [45] M. Viitala, O. Cramariuc, T. Rantala, V. Golovanov, Small hydrocarbon adsorbates on SnO_2 (110) surfaces: Density functional theory study, *Surf. Sci.* 602 (2008) 3038–3042.